

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 12657 (1989): Rubber and plastics hoses - Sub-ambient temperature flexibility tests [PCD 13: Rubber and Rubber Products]



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

BLANK PAGE



Indian Standard

RUBBER AND PLASTICS HOSES — SUB-AMBIENT TEMPERATURE FLEXIBILITY TESTS

भारतीय मानक

रबड़ और प्लास्टिक के होज — परिवेश से कम तापमान पर नम्यता परीक्षण

UDC 621·643·3 : [678·4/·8] : 620·174·251

© BIS 1989

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

Indian Standard

RUBBER AND PLASTICS HOSES — SUB-AMBIENT TEMPERATURE FLEXIBILITY TESTS

NATIONAL FOREWORD

This Indian Standard, which is identical with ISO 4672 : 1988 'Rubber and plastics hoses — Sub-ambient temperature flexibility tests' issued by the International Organization for Standardization (ISO) was adopted by the Bureau of Indian Standards on 21 April 1989, on the recommendation of the Rubber Products Sectional Committee (PCDC 13) and approval of the Petroleum, Coal and Related Products Division Council.

Indian Standard IS 443 : 1975 'Methods of sampling and test for rubber hoses' (*second revision*), has already been formulated to prescribe methods of sampling and test for rubber hoses. Reference has been given to IS 443 : 1975 in standards on thermoplastics hoses for a number of tests such as, bore size, lining and cover thickness and pressure tests. However, there are a number of other methods of tests to which hoses, both rubber and plastics, are being subjected to and are not covered in IS 443 : 1975. Therefore, it has been decided to adopt ISO test method standards, wherever available. IS 443 : 1975 will be revised in due course to update and align it with international standards to the extent possible.

The text of ISO standard has been approved as suitable for publication as Indian Standard without deviations. Certain conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- a) Wherever the words 'International Standard' appear referring to this standard, they should be read as 'Indian Standard'.
- b) Comma (,) has been used as a decimal marker while in Indian Standards, the current practice is to use a point (.) as the decimal marker.

CROSS REFERENCE

In this Indian Standard, the following International Standard is referred to. Read in its place the following:

<i>International Standard</i>	<i>Indian Standard</i>	<i>Degree of Correspondence</i>
ISO 1402 : 1984 Rubber and plastics hoses and hose assemblies — Hydrostatic testing	Clause 8 of IS 443 : 1975 Methods of sampling and test for rubber hoses (<i>second revision</i>)	Technically equivalent

The Sectional Committee, responsible for the preparation of this standard has reviewed the provisions of the following ISO standards and has decided that they are acceptable for use in conjunction with this standard:

ISO 471 : 1983 Rubber — Standard temperatures, humidities and times for the conditioning and testing of test pieces.

ISO 3383 : 1985 Rubber — General directions for achieving elevated or subnormal temperatures for test purposes.

As in the Original Standard, this Page is Intentionally Left Blank

1 Scope

This International Standard specifies two methods for assessing whether a rubber or plastics hose retains adequate flexibility at sub-ambient temperatures.

Method A is applicable to non-collapsible hose with a bore size up to and including 25 mm. It measures the increase in stiffness compared to the flexibility at a standard laboratory temperature.

Method B is a simpler, qualitative method suitable for control testing and is applicable to hose with a bore size up to and including 100 mm.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 471 : 1983, *Rubber — Standard temperatures, humidities and times for the conditioning and testing of test pieces.*

ISO 1402 : 1984, *Rubber and plastics hoses and hose assemblies — Hydrostatic testing.*

ISO 3383 : 1985, *Rubber — General directions for achieving elevated or subnormal temperatures for test purposes.*

3 Method A — Sub-ambient temperature stiffness test

3.1 Apparatus (see the figure)

3.1.1 Torque wheel, having a diameter equal to twice the minimum bend radius specified for the hose, or equal to 12 times the nominal bore of the hose, provided with equipment for holding the hose tangential to the wheel, a suitable device to bend the hose around the wheel, and a strain gauge and graphical recorder to measure the torque with an accuracy of $\pm 3\%$.

3.1.2 Cooling container, equipped with an agitator, a temperature-measuring device and a roller having a diameter of 50 mm for guiding the hose.

The coolant shall not affect the hose to be tested and shall be used as prescribed in ISO 3383.

A suitable coolant liquid is methanol or ethanol with crushed dry ice (solid carbon dioxide) added. Gaseous coolants may be employed when the design of the apparatus is such that tests using such coolants give results equivalent to those obtained with liquid coolants.

3.2 Test specimens

3.2.1 Type

The test specimens shall be cut from the hose under test and shall have a length equal to

$$2(\pi R + d)$$

where

R is the minimum bend radius as specified in the relevant hose product standard;

d is the hose bore.

3.2.2 Number

At least three test specimens shall be used for each test.

No test shall be carried out less than 24 h after manufacture of the hose.

3.3 Test temperature

The test shall be conducted at one of the following temperatures:

$$\begin{aligned} &0\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C} \\ &-10\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C} \\ &-25\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C} \\ &-40\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C} \\ &-55\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C} \end{aligned}$$

or at any other sub-ambient temperature as defined in the relevant product standard.

3.4 Procedure

Clamp one end of the test specimen (3.2) on the wheel (3.1.1), with the rest of the specimen straight. If the hose has natural curvature, this curvature shall follow that of the wheel.

Without coolant in the container (3.1.2), determine the torque required to bend the test specimen through 180° round the

wheel at the standard temperature chosen from those given in ISO 471. The time for bending shall be $12 \text{ s} \pm 2 \text{ s}$. Repeat the test with the container filled with coolant at the chosen test temperature (see 3.3). Condition the test specimen in a cold chamber at the test temperature for 24 h, followed by conditioning at the test temperature in the apparatus for at least 30 min before testing.

3.5 Expression of results

For each test specimen, calculate the mean torque at the standard temperature and the mean torque at the test temperature by calculating the mean of the peak values contained in the central 50 % of the respective torque traces.

Calculate the stiffness S , expressed as the ratio of the mean torque at the test temperature to that at the standard temperature, from the equation

$$S = \frac{T_t}{T_0}$$

where

T_t is the torque at the test temperature (mean value from three tests);

T_0 is the torque at the standard temperature (mean value from three tests).

If the individual values for the three test specimens do not agree to within 15 % of the mean value at each temperature, the test shall be repeated.

3.6 Test report

The test report shall include the following particulars:

- a) reference to this International Standard;
- b) a full description of the hose and its origin;
- c) the dimensions of the test specimens;
- d) the coolant used;
- e) the standard temperature and the test temperature;
- f) the torque at the standard temperature and at the test temperature;
- g) the calculated value of the stiffness.

4 Method B — Cold bend test

4.1 Apparatus

4.1.1 Mandrel, having an outside diameter equal to twice the minimum bend radius specified for the hose, or a former with an arc of at least 180° . If the minimum bend radius is not specified, the mandrel or former shall have an outside diameter equal to 12 times the nominal bore of the hose.

4.1.2 Conditioning chamber, capable of being maintained at the specified temperature (see 4.3).

4.2 Test specimen

The test specimen shall be cut from the hose under test and shall have a length adequate to provide a grip at each end in addition to a section which can be bent round the periphery of the mandrel.

The test specimen shall be discarded on completion of the test.

4.3 Test temperature

The test shall be conducted at one of the following temperatures:

- 0 °C \pm 2 °C
- 10 °C \pm 2 °C
- 25 °C \pm 2 °C
- 40 °C \pm 2 °C
- 55 °C \pm 2 °C

or at any other sub-ambient temperature as defined in the relevant product standard.

4.4 Procedure

Condition the mandrel (4.1.1) and the test specimen (4.2) in the conditioning chamber (4.1.2) at the chosen test temperature (see 4.3) for 24 h. Without removing them from the conditioning chamber, bend round the mandrel hoses of up to and including 22 mm bore size through 180° in $10 \text{ s} \pm 2 \text{ s}$ and hoses of greater than 22 mm bore size through 90° in $10 \text{ s} \pm 2 \text{ s}$.

For hoses of greater than 22 mm bore size, testing outside the conditioning chamber is permitted, but precautions shall be taken against an unacceptable increase in the temperature of the specimen during the test.

Observe whether any cracking or breaking of the hose lining or cover occurs.

After bending, allow the test specimen to regain ambient temperature, and apply the specified proof test pressure, measured accurately in accordance with ISO 1402, to confirm whether or not any cracking or breaking of the lining or cover has occurred.

4.5 Test report

The test report shall include the following particulars:

- a) a reference to this International Standard;
- b) a full description of the hose and its origin;
- c) the dimensions of the test specimen;
- d) the test temperature;
- e) the results of the visual examination of the test specimen after bending;
- f) the results of the visual examination after the proof pressure test;
- g) a description of the test procedure.

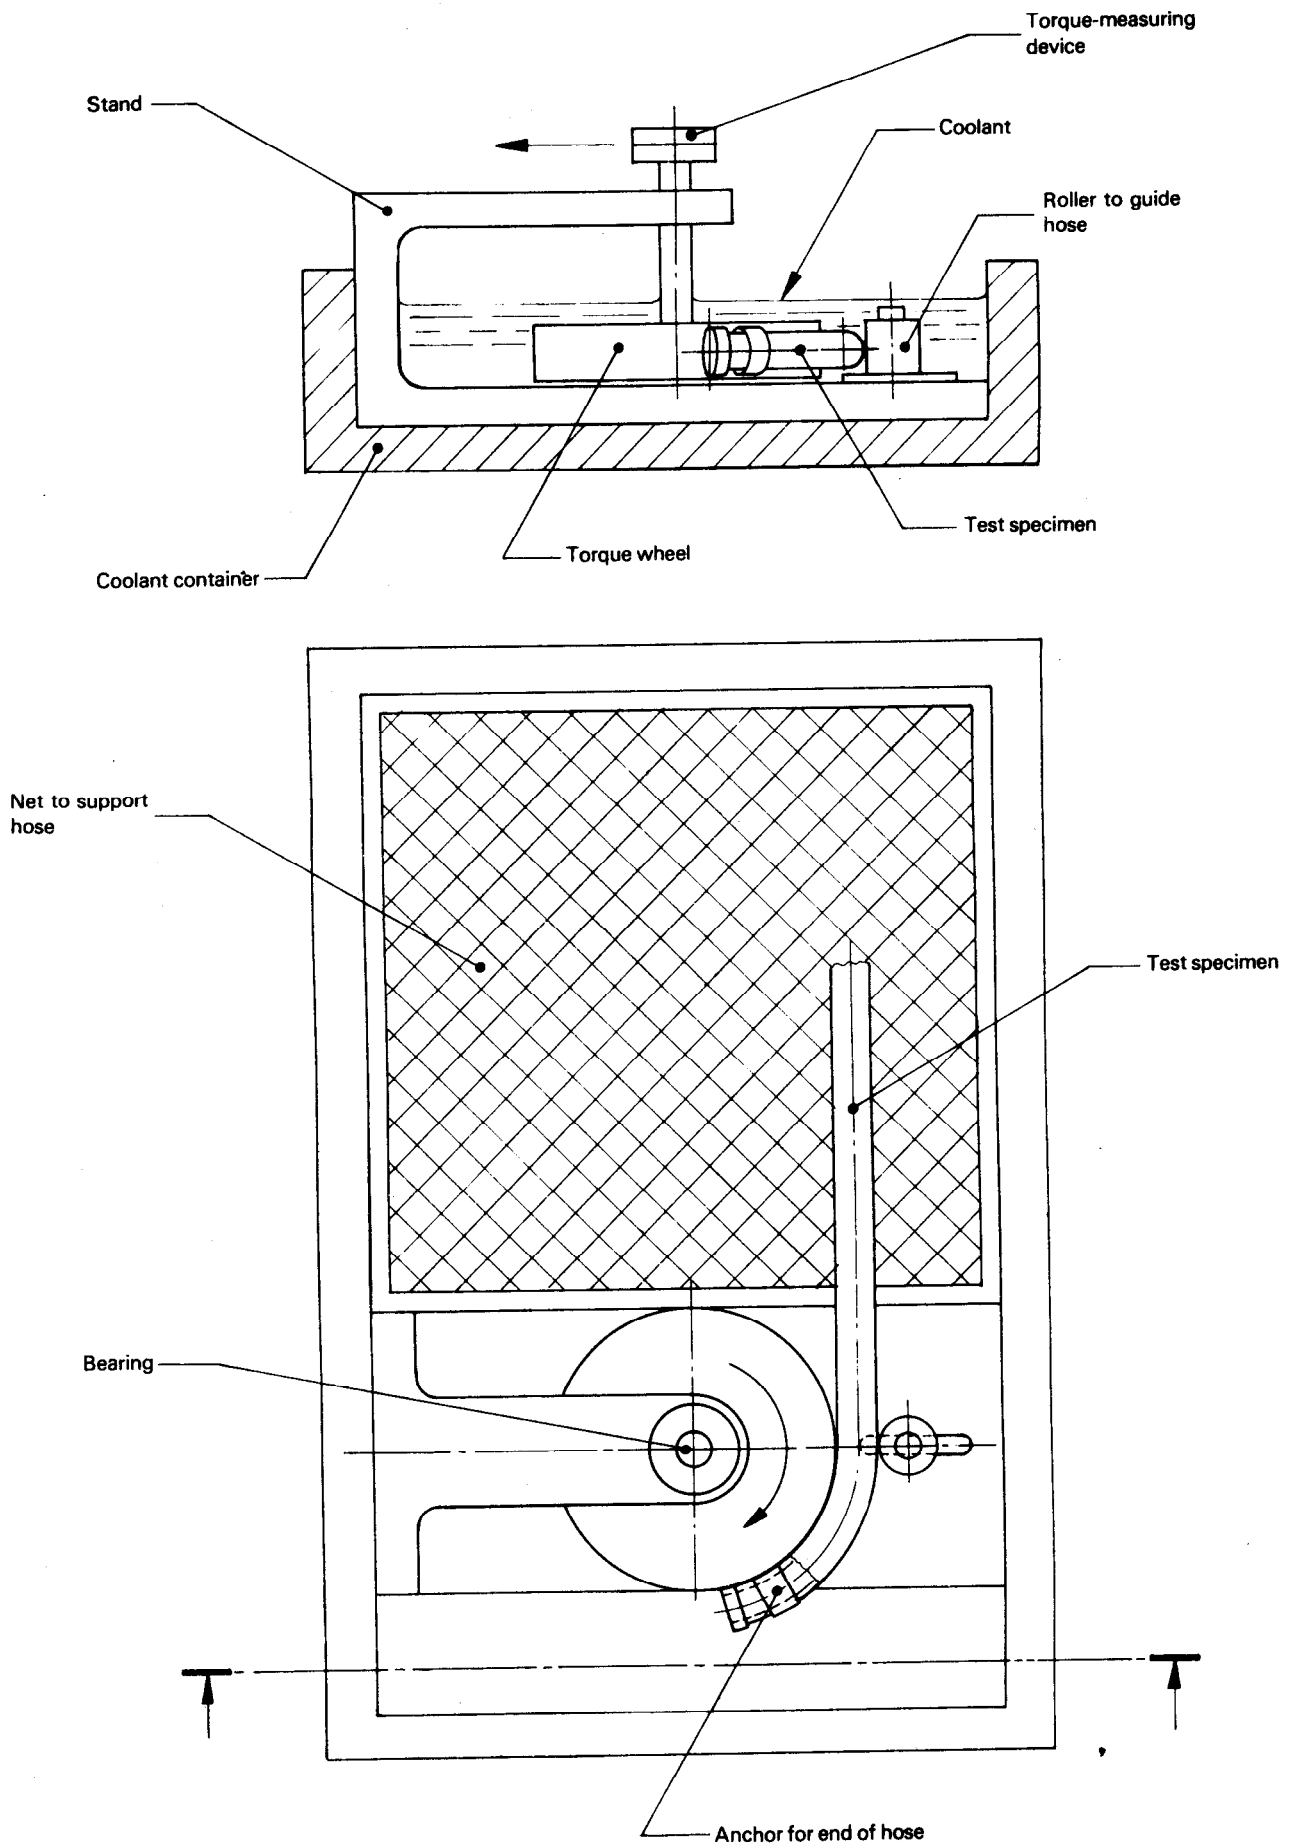


Figure 1 — Apparatus for method A

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

Revision of Indian Standards

Indian Standards are reviewed periodically and revised, when necessary and amendments, if any, are issued from time to time. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition. Comments on this Indian Standard may be sent to BIS giving the following reference :

Doc : No. PCDC 13 (1004)

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters :

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones : 331 01 31, 331 13 75

Telegrams : Manaksanstha
(Common to all Offices)

Regional Offices :

Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg
NEW DELHI 110002

Telephone
{ 331 01 31
{ 331 13 75

Eastern : 1/14 C. I. T. Scheme VII M, V. I. P. Road, Maniktola
CALCUTTA 700054

36 24 99

Northern : SCO 445-446, Sector 35-C, CHANDIGARH 160036

{ 2 18 43
{ 3 16 41

Southern : C. I. T. Campus, IV Cross Road, MADRAS 600113

{ 41 24 42
{ 41 25 19
{ 41 29 16

Western : Manakalaya, E9 MIDC, Marol, Andheri (East)
BOMBAY 400093

6 32 92 95

Branches : AHMADABAD. BANGALORE. BHOPAL. BHUBANESHWAR.
GUWAHATI. HYDERABAD. JAIPUR. KANPUR. PATNA.
TRIVANDRUM.